

Evaluation of the Cytotoxicity and Apoptotic Effects of Nano Triple Antibiotic Paste with Nano Anti-Inflammatory Drug as an Intracanal Medicament

 Yousra NASHAAT,  Hadil SABRY,  Soha Ahmed HASSAN

ABSTRACT

Objective: The aim of this study is to compare the cytotoxicity of triple antibiotic paste (TAP) with an anti-inflammatory drug (TAP+Catafast-TAPC) in nano and regular formulations versus calcium hydroxide as intracanal medicaments.

Methods: The TAPC drugs extraction were made in cell culture media MEM-E (Eagle's minimal essential medium) using concentration of 10 mg/mL of each sample for seven days. Inhibitory concentrations (IC₅₀ values) were determined for each extract. A human fibroblasts cell line was used to evaluate the cytotoxicity of different concentrations (10, 0.625 and 0.07 mg/mL) using MTT assay. The cell viability was measured after 24 h, 48 h and 7 days for all concentrations of the drugs. Flow cytometry analysis was carried out to identify the effect of materials on apoptosis/necrosis. Statistical analysis for the obtained results was done by one-way ANOVA.

Results: The results revealed that cell viability was inversely proportional to the duration of treatment in all of the groups. Calcium hydroxide (Control group) demonstrated a significantly greater cytotoxic effect, followed by Nano Triple Antibiotic Paste with Catafast as an anti-inflammatory drug (Nano TAPC), while Triple Antibiotic Paste with Catafast (TAPC) had the least cytotoxic effect. Nano TAPC has the greatest apoptotic value, while TAPC had the least when compared with the reference group, with no significant difference between groups ($P < 0.05$).

Conclusion: The cytotoxic effect of Nano TAPC was lower than that of calcium hydroxide and higher than that of TAPC. Although Nano TAPC has the highest apoptotic value when compared to TAPC and calcium hydroxide but still there is no statistically significant difference between them.

Keywords: Apoptosis, cytotoxicity, flow cytometry, MTT, Nano TAPC, Root canal

Please cite this article as:

Nashaat Y, Sabry H, Hassan SA. Evaluation of the Cytotoxicity and Apoptotic Effect of Nano Triple Antibiotic Paste with Nano Anti-Inflammatory Drug as an Intracanal Medicament. *Eur Endod J* 2021; 6: 82-9

From the Department of Endodontic, Faculty of Dentistry (Y.N. ✉ yousranashaat@hotmail.com), University of October 6, Cairo, Egypt; Department of Dental Biomaterials, Faculty of Dentistry, (H.S.), University of October 6, Cairo, Egypt; Department of Histology, Faculty of Dentistry (S.A.H.), University of October 6, Cairo, Egypt

Received 08 September 2020,
Accepted 22 November 2020

Published online: 12 March 2021
DOI 10.14744/eej.2020.29292

This work is licensed under a Creative Commons Attribution-NonCommercial 4.0 International License.



HIGHLIGHTS

- The application of nanoparticles appears promising for their ability to enhance the properties of the material.
- Although Nano TAPC is claimed to have significantly effective antimicrobial activity when used as intracanal medicament, it also had the highest cytotoxic effect when compared to TAPC and Ca(OH)₂.

INTRODUCTION

Microbial infection is the main aetiological factor of pulp and periradicular diseases. Invasion of the root canal system via microbial irritants leads to infection, necrosis and apical periodontitis (1).

Removal of microbial irritants from the root canal system and dentinal tubules and prevention of recontamination are the pertinent to

successful root canal treatment (2). This is achieved by several steps of root canal instrumentation procedures (3). However, current mechanical instrumentation techniques alone cannot completely eliminate the bacterial biofilms from the root canal; therefore, irrigants and medicaments are used to disinfect inaccessible areas irrigants do not disinfect in between appointments (4).

A number of challenges exist for achieving these goals including; the complexity of root canal system, limitations of intracanal medicaments and irrigants in eliminating the bacteria (5), in addition to complex microbial biofilms which are hard to be removed by the conventional root canal disinfection protocols (6).

Irrigants can act for a short duration while intracanal antiseptic medicaments can act for longer time against microorganisms within the root canal. Despite of their extreme importance, the root

canal irrigants and medicaments still have cytotoxic effects. Therefore, it is essential to develop effective and safe disinfecting strategies in endodontic procedures (7).

The chemical nature of medicaments employed for root canal disinfection are varied; they come from different groups, different chemicals or combinations of drugs. Antibacterial intracanal medication is expected to be effective throughout its application period and to penetrate the dentinal tubules (7, 8).

The most common used intra canal medicament is calcium hydroxide [Ca(OH)₂], which can destroy the bacterial cell membrane due to its high pH. Many other materials have been introduced as intracanal medicaments such as Chlorhexidine (CHX), triple antibiotic paste (TAP), and silver containing medicaments (8).

Nowadays, the rapid development of nanotechnology helps to develop powerful tools for various biomedical applications. Nanomaterials have gained popularity as antibacterial agents as a result of their broad-spectrum activity and biocompatibility. Nanoparticles in the range of 10 to 100 nm have been known to have bactericidal effects (9).

Irrigant solutions and intracanal medicaments may contact the periapical tissues, either through extrusion from the apex or leaching. Then it should be biocompatible and induce bone healing (10). Despite the wide application of nanoparticles to intracanal medicaments, there is a lack of information concerning their impact on human health and this gap in knowledge regarding the potential cytotoxic effect on human mesenchymal stem cells has to be evaluated (11).

Cytotoxicity is defined as the capacity of a material to impact cellular viability and can be measured at various physiological endpoints such as reduction in cell growth and proliferation, necrosis, apoptosis, or combinations of these aspects. Evaluation of cytotoxic activity of intracanal medicaments is of great importance as it affects the biological and physiological behavior of these cells (12).

Therefore, this study aimed to evaluate the cytotoxicity of newly introduced nano triple antibiotic paste with nano anti-inflammatory drug as intra canal medicaments.

MATERIALS AND METHODS

This study was approved by the ethics committee (Faculty of Dentistry, October 6 University, Cairo Egypt) number 4-2020.

Intracanal medicaments used in this study with their specifications, compositions, manufacturers as well as the technique of formation of nanomaterials are listed in Table 1.

Characterization of particles

Transmission electron microscope (TEM) (JEOL JEM 2100, Tokyo, Japan) at 200 Kv was used to identify the size and shape of the nanoparticles (Fig. 1a, b). The particle size was found to be in the range of 10 to 40 nm.

The NTAPC particles were white in color, powder in form and when tested for solubility it showed dispersion in water.

Scanning electron microscope examination with higher magnifications showed the Nano TAPC particles morphology was characterized by being spherical and flake in shape varying in size with rough surface (Figs. 1c, 1d).

All tested intra canal medicaments were applied to human skin fibroblasts (HSF) 1. Cell viability after 24 and 48 h and 7 days was evaluated using an MTT assay test.

Cytotoxicity evaluation procedures

(a) Cell cultures

HSF cell line (2×10^5) were supplied from VACSERA Company, Giza, Egypt. Cells were grown in culture flasks containing Eagle's minimal essential medium (MEM-E) and supplemented with 10% fetal bovine serum (FBS), 1% nonessential amino acid solution, and 100 IU penicillin and 100 units of streptomycin in 0.9% NaCl in a humidified atmosphere of 5% CO₂, 95% air at 37°C until a confluent monolayer was achieved. (All products: Sigma-Aldrich, Corp., St. Louis, MO, USA).

Target cells were maintained in lab for further applications where growth medium was decanted and trypsin (Sigma Aldrich, USA) solution (0.25%) was added for 2-3 min. Trypsin was decanted and cells were incubated until complete dissociation of cells.

The suspended cells were counted by hemocytometer and distributed in 96 well tissue culture plates as 100µl of culture medium with cell density so 30×10^4 cells/cm² (TPPSwiss). Plates were incubated for 24-48 h at 37°C in a 5% CO₂ atmosphere to allow the cells attachment.

(b) Sample size calculation

Using ANOVA test, assuming an effect size F ratio of 0.5, type I error of 0.05 and power of 0.8, a total sample size of 30 specimens (10 per group) was required to test the difference between the three groups. The sample size was calculated using G Power software version 3.1.9.2.

A total of 30 samples were used, 10 for each intracanal medicament shown in (Table 1).

(c) Extraction procedure

Tested materials were collected aseptically under Laminar Air Flow (LAF) and suspended in MEM-E medium to obtain 10 mg/ml of each sample for 7 days. Each nano extract media was then collected using Millex-GS sterile filter with pore size 0.22 µm while 0.45 µm pore size filters were used for collection of the extract media of regular particle size samples.

(d) Determination of cytotoxic medicament concentrations

Tested medications were two-fold serially diluted in sterile test tubes. Several dilutions of the extraction media were obtained using MEM-E Medium to achieve a total of three concentrations (10, 0.625 and 0.07 mg/mL) to determine the concentration in which the cell will survive.

(e) Cytotoxicity test

1) MTT assay

Cell viability was evaluated by performing the MTT colourimetric assay. MTT 0.5 mg/cm³ was added to the pre-treated cells as 50 µL/cm³, tissue culture plates were incubated at

TABLE 1. Material specification, composition and manufacturer

Material	Specification	Composition	Manufacturer
Metapex (Control group)	Non-setting calcium hydroxide with iodoform	Calcium hydroxide, iodoform and silicon oil.	META BIOMED Co, Chungbuk, Korea.
Triple antibiotic paste (TAP)	Mixture of ciprofloxacin, metronidazole and minocycline.	Using commercially available tablets of Ciprofloxacin (Ciprofloxacin 500 mg), Metronidazole (Flagyl 500 mg) and Minocycline (Minocin 50 mg). Following the removal of the enteric coating of the tablets, the contents were ground using a mortar and pestle and mixed in an equal amounts by weight (1:1:1) in a mixing pad (100 mg of each) and then will be dissolved in 100 mL of sterile water to prepare 1 mg/mL solution of TAP in a creamy consistency	Flagyl 500 mg: (Sanofi Aventis, Cairo, Egypt) Ciprofloxacin 500 mg: (Amriya pharm, Alexandria, Egypt) Minocin 50 mg: (Sedico, Giza, Egypt)
Catafast	50 mg NSAIDs granules for oral solution (Diclofenac potassium)	Every sachet contains 50 mg diclofenac potassium, Potassium hydrogen carbonate, mannitol; aspartame, saccharin sodium, glyceryl dibehenate, mint flavor, anise flavor.	NOVARTIS PHARMA S.A.E., Cairo, Egypt NanoTech Center (Cairo, Egypt).
Nano Triple antibiotic paste (TAP)	Mixture of nano form of ciprofloxacin, metronidazole and minocycline.	Nano TAPC consists of TAPC: Ciprofloxacin (Ciprofloxacin 500 mg), Metronidazole (Flagyl 500 mg) and Minocycline (Minocin 50 mg), mixed in equal amounts by weight (1:1:1) 100 mg of each, together with the 50 mg Catafast granules. This mixture was transferred into nano structure material using Top-down technique through the combination of various processes including fine grinding, sonication homogenisation and ultrafiltration to prevent agglomeration. Ball milling was used to produce nanomaterials by mechanical attrition in which kinetic energy from a grinding medium was transferred to material undergoing reduction. Nanomaterials were put back together with compaction and consolidation in an industrial scale process to form materials with enhanced properties (13).	

37°C for 4 hours. MTT stain was decanted and stained cells were washed twice using Phosphate Buffer Solution (PBS). Developed MTT Formazan complex crystals were dissolved using Di Methyl Sulfoxide (DMSO). All readings were taken in triplicate and then optical density of dissolved crystals was measured at 570 nm using Elisa plate reader. The viability % and medication concentrations were plotted against each other.

Optical density (OD) representing the % residual living cells was determined according the following equation:

$$\text{Viability \%} = \frac{(\text{OD test} \times 100)}{\text{OD control}}$$

Number of residual living cells = (OD of treated cells / OD of untreated cells) x Number of negative control cells (1 x 10⁴ cells / 0.1 cm³). The concentration induced 50% viability/ death of treated cells; [inhibitory concentration (IC₅₀)], was calculated. The tissue culture (TC) flasks were treated with the IC₅₀

value. The treated flasks showed cytological changes and detached cells. The detached cells were collected by cold centrifugation. The pelleted cells were fixed with methanol then prepared for flow cytometry processing.

2) Flow cytometry analysis

Flow cytometric DNA analysis was done using the fluorescence-activated cell sorting [FACSCAN] flow cytometer (14).

The remaining parts of the cell pellet of the treated and control samples were transferred into a falcon tube and the cell culture medium was removed and replaced by the buffer solution of the cell cycle test. The samples were again centrifuged for 5 minutes at 300 rpm at room temperature [20 to 25°C]. The supernatant was aspirated leaving approximately 50 µL of the residual buffer in the tubes to avoid disturbing the pellet at room temperature. 125 µL of solution 'A' containing trypsin was added to digest the cell membrane for 10 minutes. 125 µL of solution 'B' contacting trypsin in-

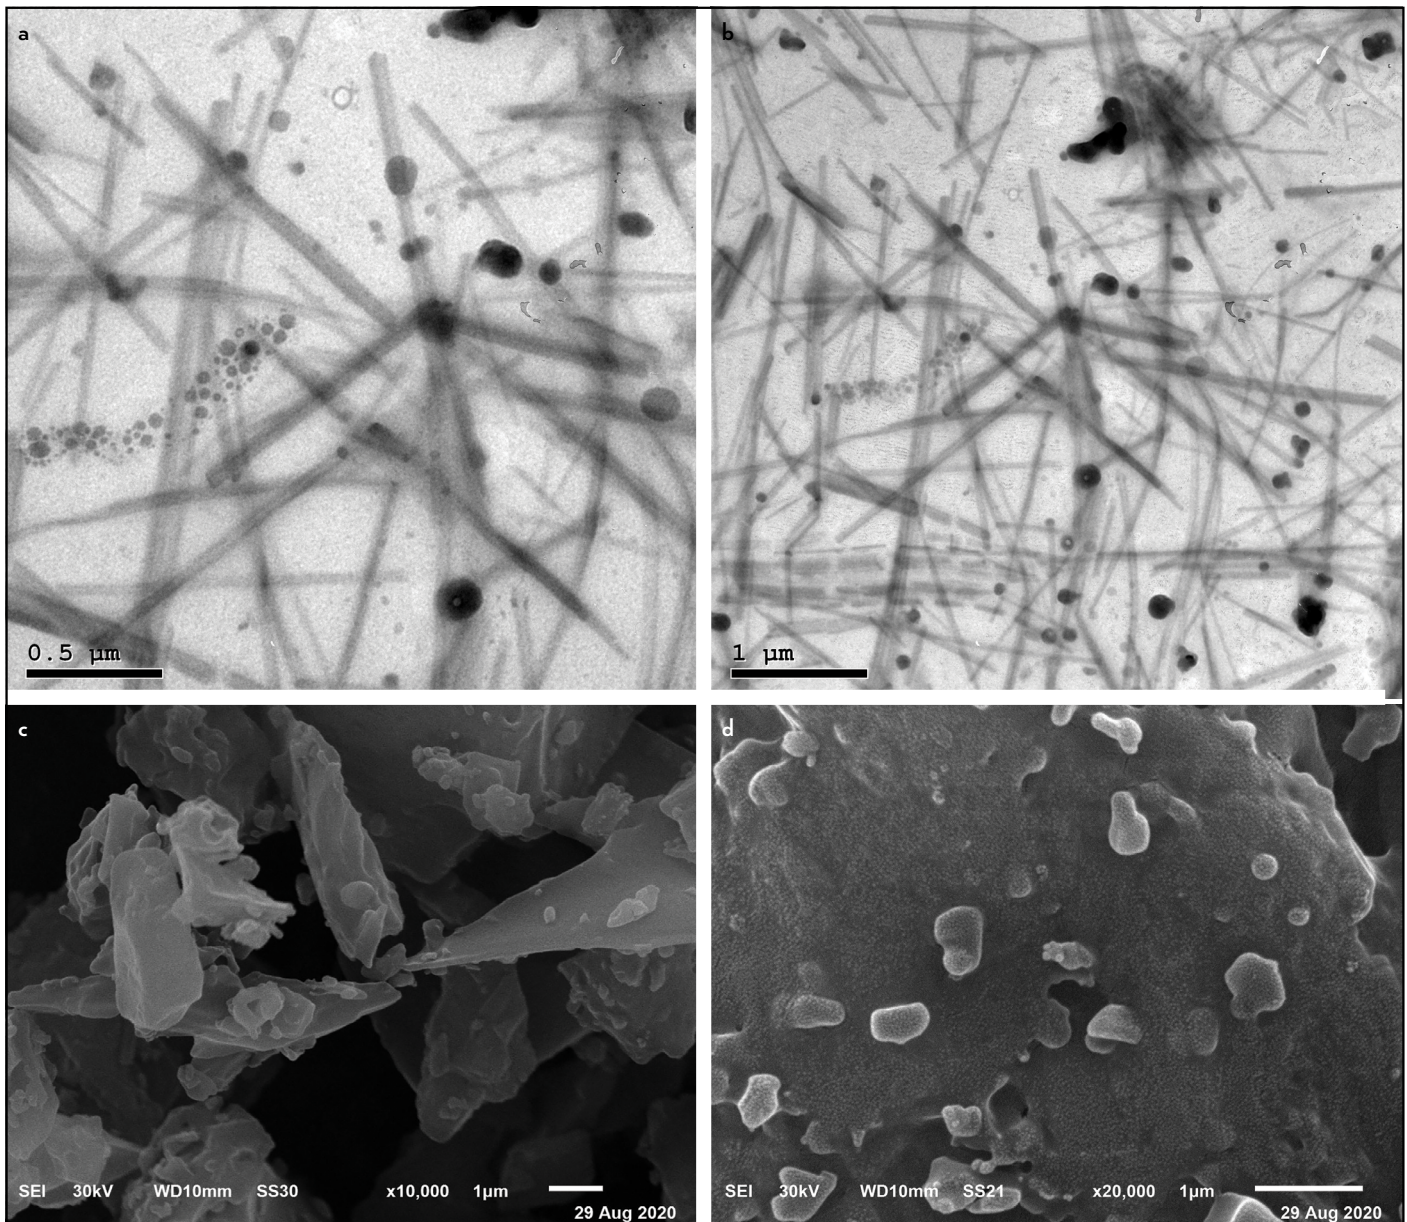


Figure 1. (a) Transmission electron microscope micrograph (TEM) of TAP nanoparticles with scale bar is 0.5 μm . (b) Transmission electron microscope micrograph (TEM) of TAP nanoparticles with scale bar 1 μm . (c) Scanning electron microscope micrograph (SEM) of TAP nanoparticles with scale bar 1 μm . (d) Scanning electron microscope (SEM) of TAP nanoparticles with scale bar 1 μm

hibitor was added for another 10 minutes to stop the action of trypsin in solution 'A'. The tubes were wrapped with tin foil to protect them from light and 125 μL of solution 'C' was added and the tubes were kept in ice bath for at least ten minutes till running in the flow cytometer within a maximum 2-3 hours.

- **Annexin V stain**

Annexin V Apoptosis Detection Kit is based on the observation of initiated apoptosis. Cells translocate the membrane phosphatidylserine [PS] from the inner face of the plasma membrane to the cell surface. Once it reached the cell surface, PS can be easily detected by staining with a fluorescent conjugate [Annexin V]; a protein that has a high affinity for PS. The one-step staining procedure takes only 10 minutes. Detection can be analyzed by flow cy-

tometry. The kit can differentiate between apoptosis and necrosis when performing both Annexin V and Propidium iodide [PI] staining.

- **Annexin V-FITC assay protocol**

Incubation of cells with Annexin V-FITC:

1. Apoptosis was induced by test medications using flowcytometry.
2. Cells were collected by centrifugation and desired cell count was optimized as $2 \times 10^5/\text{ml}$ using hemocytometer.
3. Cells were re-suspended in 500 μl of 1X Binding Buffer.
4. Annexin V-FITC and 5 μl PI 50 mg/ml of were added.
5. Stained cells were incubated at room temperature for 5 min in the dark.

Flow cytometry analysis

Apoptotic profile traced using Annexin -V and PI stains using flow cytometry, [Ex=488 nm; Em=530 nm] using FITC signal detector [usually FL1] and PI staining by the phycoerythrin emission signal detector [usually FL2].

Statistical analysis

Statistical analysis Data presented as mean and standard deviation (SD) when appropriate. Data Explored for Normality using D'Agostino-Pearson test. The significance level was set at $P \leq 0.05$ ($\alpha = 0.05$). Two-Way ANOVA test was used to compare between tested materials at different concentrations and times. Statistical analysis was performed with IBM® SPSS® (SPSS Inc., IBM Corporation, NY, USA) Statistics Version 25 for Windows.

RESULTS

1) MTT assay

(a) Inhibitory concentration (IC50 values)

The inhibitory concentration of TAPC, Nano TAPC and $\text{Ca}(\text{OH})_2$ were calculated from the regression curve of log concentration versus the cell viability (%). The estimated IC 50 values for the tested intracanal medicaments after 24 hours were 6.147, 4.430 and 2.028 mg/ml respectively (Fig. 2).

(b) Percentage of viability values

The effect of different intracanal medicaments on percentage of viability of fibroblast cells value are listed in Tables 2-4, and Figs. 3-5.

2) Flow cytometry test results

(a) Apoptotic effect evaluation of intra canal medicaments

The mean values of apoptotic and necrotic cells in cultures assessed using flow cytometry analysis for different intracanal medicaments were listed in Table 5 and Figs. 6a-c.

(b) The effect of particle size (TAPC vs. Nano TAPC)

Comparison of flow cytometry test results (Mean values \pm SDs) between regular and nano scale forms for TAPC experimental group were explained in Table 6 and Fig. 7.

DISCUSSION

Intra-canal medicaments are usually applied between visits, and have several advantages. They act by inhibiting proliferation of bacteria and minimizing ingress of pathogens in between visits through a leaking temporary restoration (15).

Calcium hydroxide as an intracanal medicament, has been successfully used in endodontic treatment for decades. It can stimulate the formation of calcified tissue, to induce antibacterial properties and to disinfect root canals after one month of application in 97% of treated cases (16).

Another combination of antibiotics, called TAP was introduced especially for the regeneration and revascularization protocol and the treatment of open apex teeth with necrotic pulp. This material has also shown other applications in endodontics. Several studies have reported the antibacterial efficacy of TAP containing ciprofloxacin, metronidazole, and doxycycline against the pathogens commonly found inside the root canal

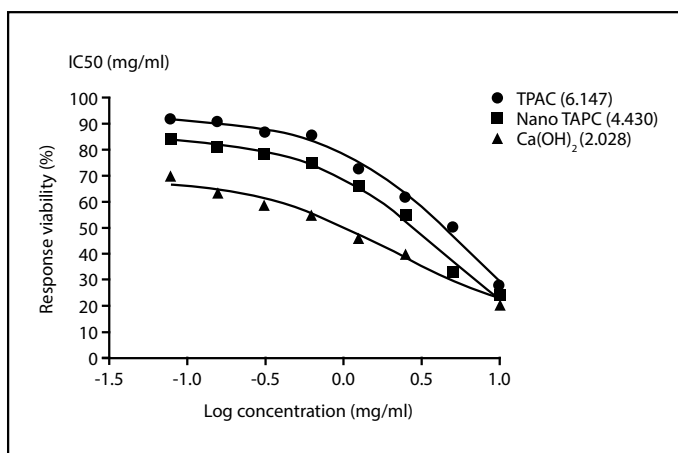


Figure 2. Graph showing the inhibitory concentration (IC50) values of all tested intra canal medicaments after 24 hours

TABLE 2. Cytotoxicity test results measured by % of viable cells of all groups at different time intervals for (Conc. 10mg/ml)

	Conc. 10 mg/ml			P value
	24 h	48 h	7 days	
TAPC	27.98 ^{Aa}	26.40 ^{Aa}	22.93 ^{Ab}	0.305 ns
Nano TAPC	24.14 ^{Aa}	22.93 ^{Ba}	19.92 ^{Ca}	0.018*
$\text{Ca}(\text{OH})_2$	20.40 ^{Ab}	19.19 ^{Ab}	17.82 ^{Ac}	0.079 ns
P value	<0.001*	<0.001*	0.027*	

*: Significant ($P < 0.05$), ns: non-significant ($P > 0.05$). Different capital letters mean statistical significance in rows. Different small letters mean statistical significance in columns

TABLE 3. Cytotoxicity test results measured by % of viable cells of all groups at different time intervals for (Conc. 0.625mg/ml)

	Conc. 0.625 mg/ml			P value
	24 h	48 h	7 days	
TAPC	85.16 ^{Ab}	81.87 ^{Aa}	67.62 ^{Ab}	0.365ns
Nano TAPC	74.20 ^{Ac}	59.39 ^{Ba}	56.65 ^{Ca}	<0.001*
$\text{Ca}(\text{OH})_2$	54.83 ^{Aa}	52.91 ^{Bb}	48.40 ^{Cc}	0.004*
P value	<0.001*	<0.001*	<0.001*	

*: Significant ($P < 0.05$), ns: non-significant ($P > 0.05$). Different capital letters mean statistical significance in rows. Different small letters mean statistical significance in columns

TABLE 4. Cytotoxicity test results measured by % of viable cells of all groups at different time intervals for (Conc. 0.07mg/ml)

	Conc. 0.07 mg/ml			P value
	24 h	48 h	7 days	
TAPC	91.65 ^{Ab}	86.77 ^{Bb}	85.62 ^{Cb}	0.002*
Nano TAPC	84.52 ^{Ab}	83.43 ^{Aa}	78.49 ^{Ab}	0.138ns
$\text{Ca}(\text{OH})_2$	69.82 ^{Ac}	63.24 ^{Bc}	57.21 ^{Cc}	<0.001*
P value	<0.001*	<0.001*	<0.001*	

*: Significant ($P < 0.05$), ns: non-significant ($P > 0.05$). Different capital letters mean statistical significance in rows. Different small letters mean statistical significance in columns

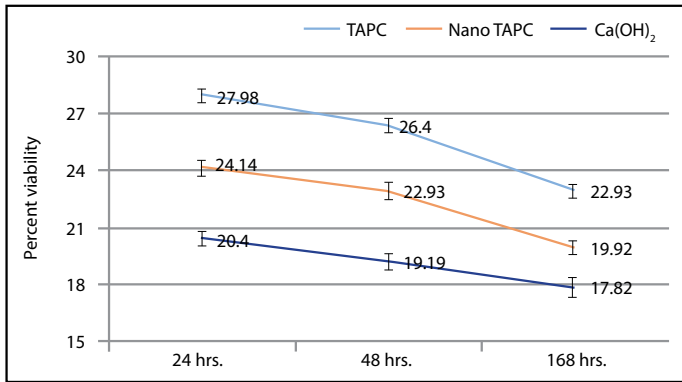


Figure 3. Line graph showing the mean values of % viability (± SD) of all groups at different time intervals for (Conc. 10mg/ml)

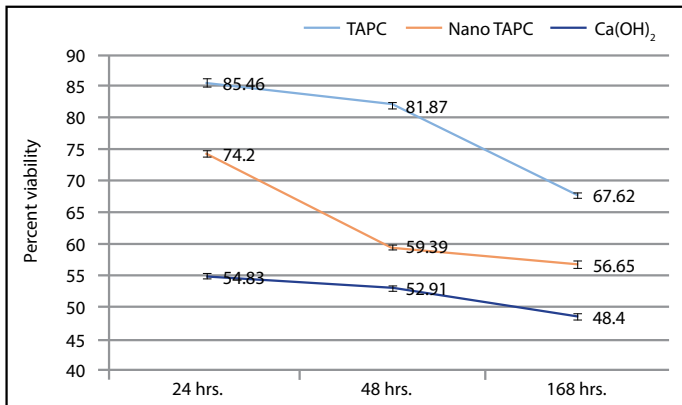


Figure 4. Line graph showing the mean values of % viability (±SD) of all groups at different time intervals for (Conc. 0.65 mg/ml)

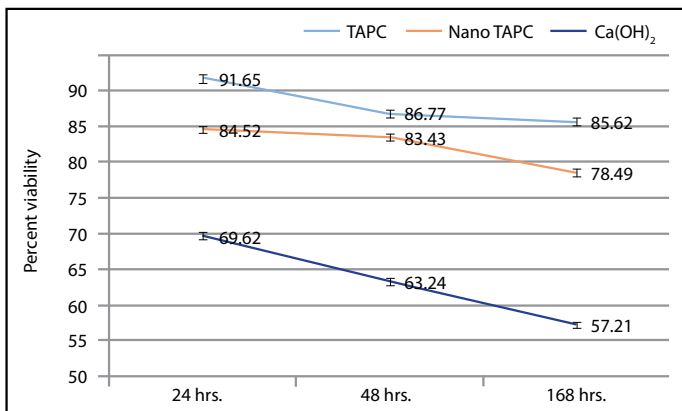


Figure 5. Line graph showing the mean values of % viability (±SD) of all groups at different time intervals for (Conc. 0.07 mg/ml)

TABLE 5. Percentage of apoptotic and necrotic cells in cultures assessed by using flow cytometry analysis for different intracanal medicaments

Variables	Early apoptosis	Late apoptosis	Necrosis
TAPC	2.35±0.070	3.17±0.098	1.61±0.104
Nano TAPC	7.23±0.104	3.65±0.128	2.14±0.087
Ca(OH) ₂	5.91±0.268	13.26±0.854	3.28±0.072
P value	<0.001*	<0.001*	<0.001*

*: Significant from control group (P<0.05), ns; non-significant from control group

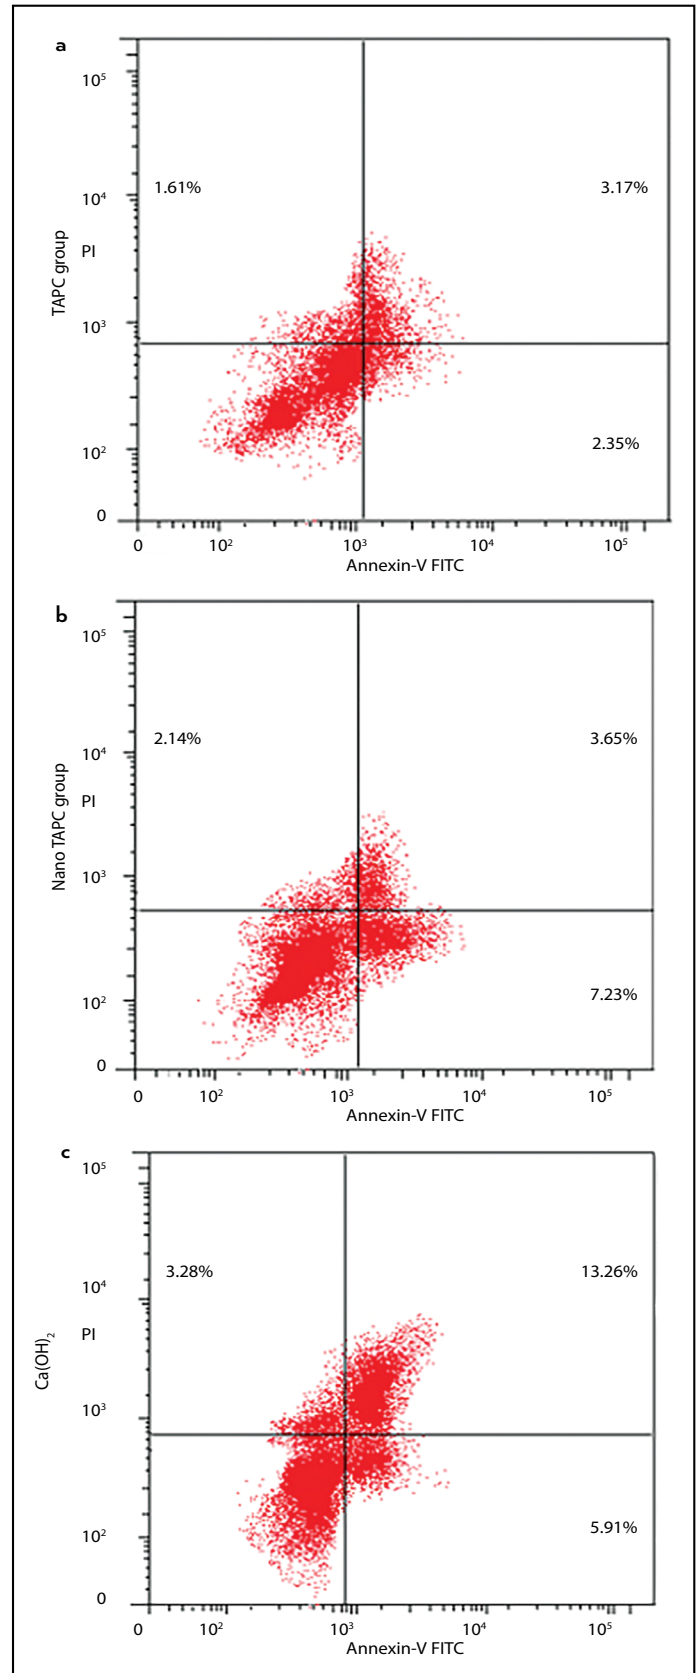


Figure 6. (a-c) The dot plots are representative of control and human fibroblast cells exposed to various intra canal medicaments, representing the populations of viable cells [bottom left: annexin V⁻, propidium iodide (PI⁻), early apoptotic (bottom right: annexin V⁺, PI⁻), late apoptotic (top right: annexin V⁺, PI⁺), and necrotic (top left: PI⁺) cells. The x-axis is the fluorescence intensity of annexin-V; the y-axis is the fluorescence intensity of PI

TABLE 6. Comparison of flowcytometry test results (Mean values±SDs) between TAPC and Nano TAPC experimental groups

Variables	Early apoptosis	Late apoptosis	Necrosis
TAPC	2.350.070 ^a	3.170.098 ^a	1.610.104 ^a
Nano TAPC	7.230.104 ^b	3.650.128 ^b	2.140.087 ^b
P value	<0.001*	0.006*	0.003*

*: Significant (P<0.05), ns: non-significant (P>0.05)

Different small letters mean statistical significance in column

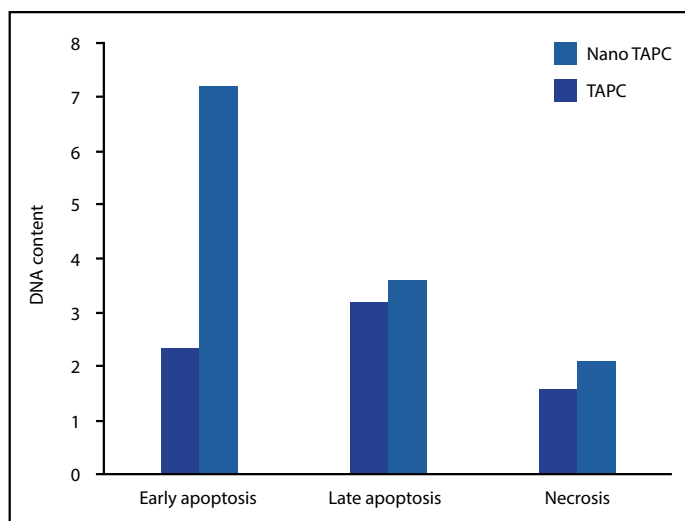


Figure 7. Bar chart showing flowcytometry early, late apoptosis and necrosis values of TAPC and Nano TAPC

system including *Enterococcus faecalis*. Because of complexity of the root canal infection, a combination of antibiotics may be needed to address the diverse flora encountered in root canal infections (17).

Salem-Milani et al. (18) was the first to comparatively evaluate anti-bacterial efficiency of ibuprofen, diclofenac and Ca(OH)₂ using the agar diffusion test, the authors revealed the anti-bacterial properties of NSAIDs (ibuprofen, diclofenac) against *E. faecalis*; whereas Ca(OH)₂ failed at the same. The exact mechanism of antibacterial activity of diclofenac and ibuprofen remains unclarified. Studies have postulated the following mechanism(s) of action: inhibition of bacterial DNA synthesis, impairment of membrane activity, anti-plasmid activity, alteration in genes encoding transport/binding proteins as well as down-regulation of efflux pumps, reduced quorum sensing-controlled motility leading to reduced biofilm (19).

Diclofenac potassium anti-inflammatory drug was proved to be efficient in reducing post-operative pain when it was added to triple antibiotic paste as intracanal medication, its anti-inflammatory effect was comparable to that of calcium hydroxide when used in asymptomatic teeth with necrotic pulps (20).

Recently, nanotechnology has become increasingly utilized for dental applications because of their great broad-spectrum antibacterial effectiveness (21). This study aimed to evaluate the cytotoxic effects of TAP and TAP with nano-particles. Evaluation of the intracanal medicaments cytotoxicity is highly important, as it may affect the biological and physiological

behavior of the cells. Hence, the concentration of the medicaments are important for effective treatment (22).

Three different concentrations (10, 0.625 and 0.07mg/ml) of the intracanal medicaments were used at three different time intervals (24hr., 48hr. and 7 days) to assess cytotoxicity. The higher the concentration and the longer the contact time, the stronger the cytotoxic effect (23).

MTT was used for the evaluation of the cytotoxicity as it considered simple, rapid and reliable test, MTT (3-[4, 5-dimethylthiazol-2-yl]-2,5-diphenyltetrazolium bromide) is a water-soluble tetrazolium salt, which converted to an insoluble purple formazan by cleavage of the tetrazolium ring by succinate dehydrogenase (LDH) within the mitochondria. The formazan product is impermeable to the cell membranes and therefore it accumulates in healthy cells (24).

Cytotoxicity was measured using both MTT assay and flowcytometry because single cytotoxicity assay is not considered to be sufficient to evaluate or predict all aspects of the material's cytotoxicity as using a colorimetric assay to analyze a given compound do not know give sufficient indication of cytotoxicity. Flowcytometry is a stable and reliable indicator of the real cell viability, this is based on its capacity to exclude dye in the living cells. The Annexin V/ Propidium iodide (PI) protocol was used, Annexin V can assess if cells are viable, apoptotic, or necrotic through differences in plasma membrane integrity and permeability while PI does not stain live or early apoptotic cells due to presence of an intact plasma membrane (25).

Fibroblasts were used to assess cytotoxicity of intracanal medicaments, as they are more behaviour representative of *in-vivo* cells. Fibroblasts act as vital immune-regulatory cells that involved in local inflammatory and immune responses. They produce cytokines, chemokines, growth factors and other biologically active molecules, and their function may be modulated by the microenvironment (26). The results of the present study showed that the cytotoxicity was affected by the concentration and particle size of the utilized medicaments.

Calcium hydroxide showed the highest level of cytotoxicity amongst all the studied groups, this may be explained by the release of the reactive hydroxyl ions and the high pH which may cause cell necrosis and apoptosis as previously proved by Selis et al. (11) who stated that Ca(OH)₂ had cytotoxic potential against fibroblast cells.

Triple antibiotic paste showed less cytotoxic effect than calcium hydroxide. The lower cytotoxicity of TAPC may be attributed to the inhibition of cell collagenase and matrix metalloproteinase, also doxycycline increases collagen formation and angiogenesis in the process of wound healing. Hosseini et al. (27) compared the cytotoxic effect of TAP and Ca(OH)₂ against fibroblast cells and also concluded that Ca(OH)₂ had more cytotoxic effect than that of the triple antibiotic paste.

The Nano TAPC showed more cytotoxic effect on human skin fibroblast cells than its corresponding regular TAPC. This might be explained by decrease in the particle size from macroscopic to nano scale that lead to changes in physicochemical proper-

ties of the materials and resulted in particles with smaller size that may elicit different biological responses including toxicity (16, 28). Also may be from disruption of the mitochondrial respiratory chain by the nano particles leading to production of reactive oxygen species (ROS) and interruption of adenosine triphosphate (ATP) synthesis, which in turn caused DNA damage (28). Samiei et al. found slight increase in lactic acid dehydrogenase leakage which is cell damage indicator that was observed with nanoparticles, indicating that these particles interfere with cell metabolism (29). The higher cytotoxic effect of the nano TAPC intracanal medicaments could also be attributed to the ability of nanoparticles to bind to the negatively charged part of the cell membrane, causing disturbance in its functions such as permeability and respiration, causing leaking of the cytoplasmic content and eventually rupture of the cell. As a result, the nanoparticles will infiltrate inside the cytoplasmic content and interact with sulphur and phosphorus containing proteins such as DNA and RNA, causing further damage to the cell (30).

CONCLUSION

The cytotoxic effect of Nano TAPC was lower than that of calcium hydroxide and higher than that of TAPC. Although it has the highest apoptotic effect when compared to TAPC and calcium hydroxide but still there is no statistically significant difference between them.

Disclosures

Conflict of interest: The author declares that there is no conflict of interest related to this research.

Ethics Committee Approval: This was approved by the local ethics committee number 4/2020 Faculty of Dentistry, University of October 6.

Peer-review: Externally peer-reviewed.

Financial Disclosure: There is no financial involvement with any commercial organization in the subject or materials discussed in this manuscript.

Authorship contributions: Concept – Y.N.; Design – S.A.H.; Supervision – Y.N.; Funding – Y.N., H.S., S.A.H.; Materials – Y.N., H.S., S.A.H.; Data collection &/or processing – Y.N.; Analysis and/or interpretation – Y.N., S.A.H.; Literature search – H.S.; Writing – Y.N., H.S.; Critical Review – Y.N., H.S., S.A.H.

REFERENCES

- Ambikathanaya UK. Intracanal antiseptic medications; A Review. *Unique J Med Dent Sci* 2014; 2(3):136–42.
- Iqbal A. Antimicrobial irrigants in the endodontic therapy. *Int J Health Sci (Qassim)* 2012; 6(2):186–92. [CrossRef]
- Kalyan SS, Parmar G, Chandki R. Surmounting the endodontic biofilms: the nano way. *J Dent Her* 2014; 1:16–9.
- Afkhami F, Elahy S, Mahmoudi-Nahavandi A. Spectrophotometric analysis of crown discoloration following the use of silver nanoparticles combined with calcium hydroxide as intracanal medicament. *J Clin Exp Dent* 2017; 9(7):e842–7. [CrossRef]
- Mehta S, Verma P, Tikku AP, Chandra A, Bains R, Banerjee G. Comparative evaluation of antimicrobial efficacy of triple antibiotic paste, calcium hydroxide, and a proton pump inhibitor against resistant root canal pathogens. *Eur J Dent* 2017; 11(1):53–7. [CrossRef]
- Bo D, Kayombo CM. Effect of nanosilver gel, chlorhexidine gluconate, and camphorated phenol on enterococcus faecalis biofilm. *Int Sch Res Notices* 2014; 2014:380278. [CrossRef]
- Makkar S, Aggarwal A, Pasricha S, Kapur I. To evaluate the properties of silver nano particle based irrigant as endodontic root canal irrigant. *Int J Dent Heal Sci* 2014; 1:485–92.
- Mozayeni MA, Haeri A, Dianat O, Jafari AR. Antimicrobial effects of four intracanal medicaments on enterococcus faecalis: an *in vitro* study. *Iran Endod J* 2014; 9(3):195–8.
- Markan S, Lehl G, Kapoor S. Recent advances of nanotechnology in endodontics, conservative and preventive dentistry-a review. *J Dent Oral Biol* 2017; 2(10):1–4.
- Zare Jahromi M, Ranjbarian P, Shiravi S. Cytotoxicity evaluation of Iranian propolis and calcium hydroxide on dental pulp fibroblasts. *J Dent Res Dent Clin Dent Prospects* 2014; 8(3):130–3.
- Selis D, Pande Y, Smoczer C, Wheeler M, Alhabeil J, Paurazas S, et al. Cytotoxicity and genotoxicity of a new intracanal medicament, 2-hydroxyisocaproic acid-an *in vitro* study. *J Endod* 2019; 45(5):578–83. [CrossRef]
- Nogueira DR, Mitjans M, Rolim CM, Vinardell MP. Mechanisms underlying cytotoxicity induced by engineered nanomaterials: a review of *in vitro* studies. *nanomaterials (Basel)* 2014; 4(2):454–84. [CrossRef]
- Arole VM. Fabrication of nanomaterials by top-down and bottom-up approaches-an overview. *Journal of Advances in Applied Sciences and Technologies* 2014; 1:89–93.
- Chrepa V, Henry MA, Daniel BJ, Diogenes A. Delivery of apical mesenchymal stem cells into root canals of mature teeth. *J Dent Res* 2015; 94(12):1653–9. [CrossRef]
- Kumar A, Tamanna S, Iftekhar H. Intracanal medicaments – Their use in modern endodontics : A narrative review. *J Oral Res Rev* 2019; 11(2):94–9.
- Louwakul P, Saelo A, Khemaleelakul S. Efficacy of calcium oxide and calcium hydroxide nanoparticles on the elimination of Enterococcus faecalis in human root dentin. *Clin Oral Investig* 2017; 21(3):865–71. [CrossRef]
- Parhizkar A, Nojehdehian H, Asgari S. Triple antibiotic paste: momentous roles and applications in endodontics: a review. *Restor Dent Endod.* 2018; 43(3):e28. [CrossRef]
- Salem-Milani A, Balaee-Gajan E, Rahimi S, Moosavi Z, Abdollahi A, Zakeri-Milani P, et al. Antibacterial effect of diclofenac sodium on enterococcus faecalis. *J Dent (Tehran)* 2013; 10(1):16–22.
- Mazumdar K, Dastidar SG, Park JH, Dutta NK. The anti-inflammatory non-antibiotic helper compound diclofenac: an antibacterial drug target. *Eur J Clin Microbiol Infect Dis* 2009; 28(8):881–91. [CrossRef]
- Omaia M, Negm M, Nashaat Y, Nabil N, Othman A. The effect of triple antibiotic paste as an intracanal medication with an anti-inflammatory drug on post-operative pain of asymptomatic uniradicular necrotic teeth: a double blind randomized clinical trial, F1000Research 2019; 8:1687.
- Monfared AL, Soltani S, Louei A. Effects of silver nanoparticles administration on the liver of rainbow trout (*Oncorhynchus mykiss*): histological and biochemical studies. *Eur J Exp Bio* 2013; 3(2):285–9.
- Yadlapati M, Souza LC, Dorn S, Garlet GP, Letra A, Silva RM. Deleterious effect of triple antibiotic paste on human periodontal ligament fibroblasts. *Int Endod J* 2014; 47(8):769–75. [CrossRef]
- Fayyad D, Elgendy AA. Cell viability and apoptotic changes of dental pulp stem cells treated with propolis, chitosan and their nano counterparts. *Tanta Dent J* 2017; 14(4):1–16. [CrossRef]
- Labban N, Yassen GH, Windsor LJ, Platt JA. The direct cytotoxic effects of medicaments used in endodontic regeneration on human dental pulp cells. *Dent Traumatol* 2014; 30(6):429–34. [CrossRef]
- Mao Z, Liu Z, Chen L, Yang J, Zhao B, Jung YM, et al. Predictive value of the surface-enhanced resonance Raman scattering-based MTT assay: a rapid and ultrasensitive method for cell viability *in situ*. *Anal Chem* 2013; 85(15):7361–8. [CrossRef]
- Althumairy RI, Teixeira FB, Diogenes A. Effect of dentin conditioning with intracanal medicaments on survival of stem cells of apical papilla. *J Endod* 2014; 40(4):521–5. [CrossRef]
- Hosseini Matin M, Zare Jahromi M, Fesharaki M, Ostad Sharif M. Cytotoxicity of triple antibiotic paste and calcium hydroxide against cultured human dental pulp fibroblasts. *JDS* 2019; 33(3):196–204.
- Braydich-Stolle L, Hussain S, Schlager JJ, Hofmann MC. *In vitro* cytotoxicity of nanoparticles in mammalian germline stem cells. *Toxicol Sci* 2005; 88(2):412–9. [CrossRef]
- Samiei M, Torab A, Hosseini O, Abbasi T, Abdollahi AA, Divband B. Antibacterial effect of two nano zinc oxide gel preparations compared to calcium hydroxide and chlorhexidine mixture. *Iran Endod J* 2018; 13(3):305–11.
- Karczewski A, Feitosa SA, Hamer EI, Pankajakshan D, Gregory RL, Spolnik KJ, et al. Clindamycin-modified triple antibiotic nanofibers: a stain-free antimicrobial intracanal drug delivery system. *J Endod* 2018; 44(1):155–62. [CrossRef]